

Zn₄O₄ tetrameric clusters in a zinc phosphate with channels

S. Neeraj, Srinivasan Natarajan and C. N. R. Rao *

*Chemistry and Physics of Materials Unit, Jawaharlal Nehru Centre for Advanced Scientific Research, Jakkur, P.O., Bangalore 560 064, India. E-mail: cnrrao@jncasr.ac.in**Received 30th May 2000, Accepted 3rd July 2000**Published on the Web 14th July 2000*

Zn₄O₄ tetrameric clusters, found for the first time in an open-framework phosphate form basket-shaped building units, in combination with PO₄ tetrahedra give rise to a one-dimensional channel structure.

Among the open-framework metal phosphates, those of zinc constitute a large family.¹ Zinc phosphates exhibiting novel structural features, such as Zn₂O₂ dimers,² Zn₂PO₃ trimers³ and OZn₄ tetrahedral clusters,⁴ have been isolated and characterized. We have discovered Zn₄O₄ tetrameric clusters in an open-framework zinc phosphate of the formula [N₃C₄H₁₆][Zn₅(PO₄)₄] **I**. The Zn₄O₄ clusters are linked to PO₄ tetrahedra to form basket-shaped building units which are connected in such a manner as to give rise to channels.

Compound **I** was synthesized hydrothermally in the presence of diethylenetriamine (DETA). In a typical synthesis, 2.5 mM of ZnO was dispersed in 250 mM of deionized water and 5.0 mM of HCl (35%). To this, 2.5 mM of oxalic acid and 5.0 mM H₃PO₄ (aq. 85 wt.%) were added under constant stirring.

Finally, 2.5 mM of DETA was added to the above and the mixture was homogenized for 30 min. The final gel (pH *ca.* 2) was sealed in a PTFE-lined stainless steel autoclave (Parr, Moline, USA) and heated at 180 °C for 56 h. The monophasic product (70% yield based on Zn), in the form of colorless rod-like crystals, was vacuum filtered, washed with water and dried under ambient conditions. The role of oxalic acid in the formation of **I** is not clear and in its absence a layered structure was obtained.³

The structure of **I** was solved by single crystal methods employing a Siemens SMART-CCD diffractometer.⁵ The asymmetric unit contains 32 non-hydrogen atoms, of which 25 belong to the framework and 7 to the guest species [Fig. 1(a)]. The framework is built up of a network of ZnO₄ and PO₄ tetrahedra resulting in a three-dimensional architecture. The framework has the formula, [Zn₅(PO₄)₄]²⁻ and charge neutrality is achieved by the presence of a diprotonated DETA molecule, [N₃C₄H₁₆]²⁺. There is one amine molecule present per formula unit. The framework structure of **I** has several unique features,

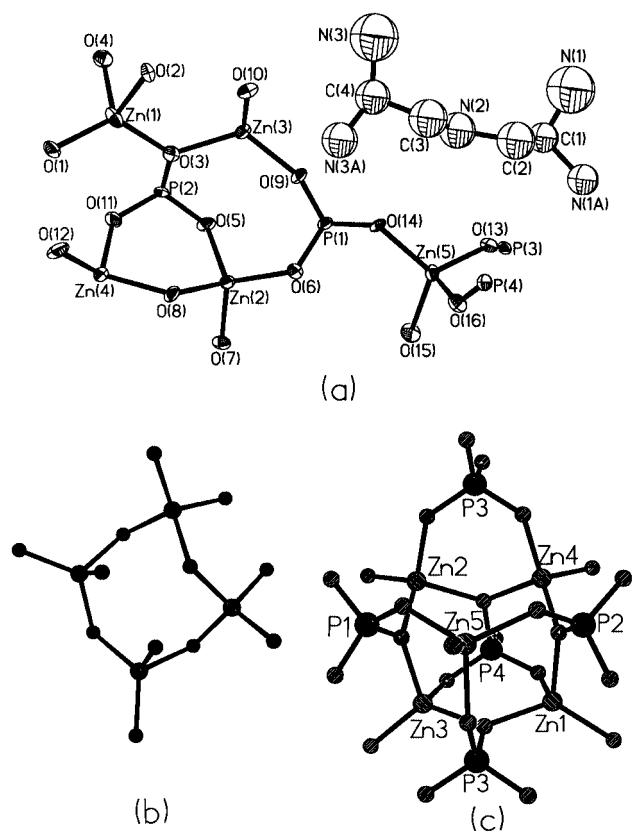


Fig. 1 (a) ORTEP plot of [N₃C₄H₁₆][Zn₅(PO₄)₄] **I**. Thermal ellipsoids are given at 50% probability, (b) the Zn₄O₄ tetramer; note the four-membered ring formation, (c) the basic building unit. Note that the connectivity between the Zn₄O₄ tetramer and the PO₄ units lead to a basket-like arrangement.

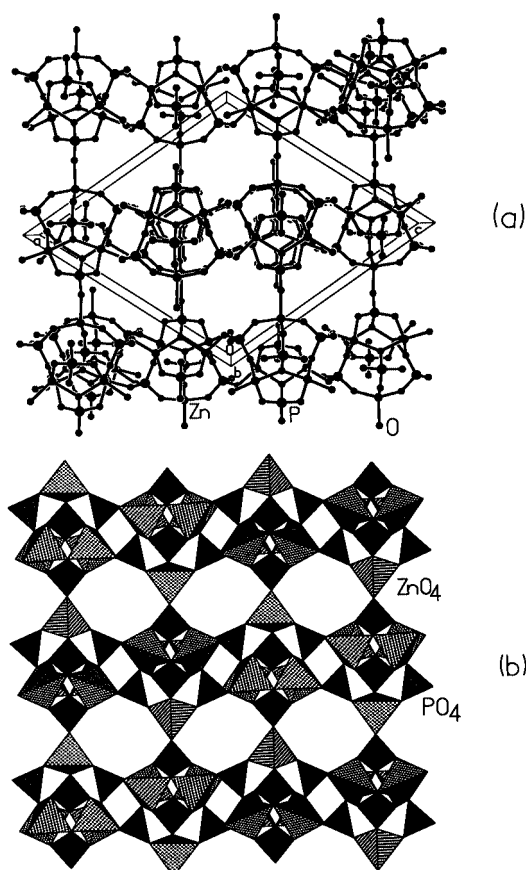


Fig. 2 Structure of [N₃C₄H₁₆][Zn₅(PO₄)₄] **I**, along the *ac* plane showing the channels: (a) ball and stick view and (b) polyhedral view. Amine molecules are not shown for clarity.

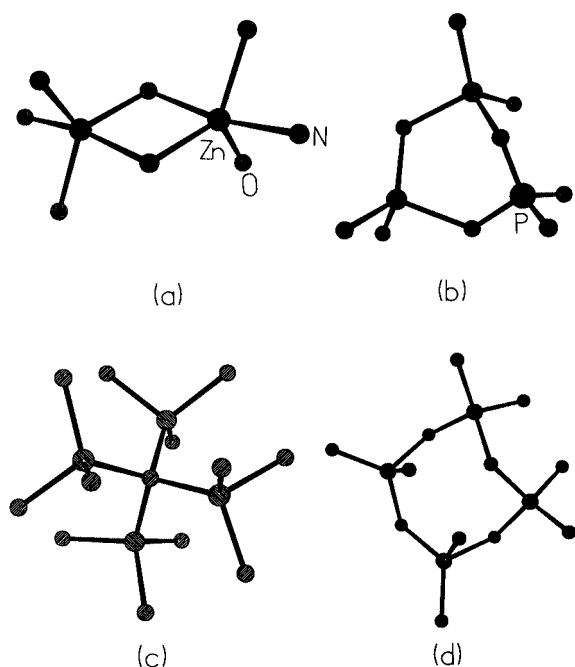


Fig. 3 Structural units observed in open-framework zinc phosphates: (a) the Zn_2O_2 dimer, (b) Zn_2PO_3 trimer, (c) OZn_4 tetrahedral clusters and (d) the four-membered Zn_4O_4 tetramer cluster.

the most important of which is the presence of the four-membered Zn_4O_4 unit formed only by Zn tetrahedra [Zn(1), Zn(2), Zn(3) and Zn(4)] linked to each other [Fig. 1(b)]. Each oxygen atom of the 4-membered Zn_4O_4 tetramer is three-coordinate being connected to a PO_4 tetrahedron [P(1), P(2), P(3) and P(4)]. The phosphate units are further linked to $\text{Zn}(5)\text{O}_4$ tetrahedra forming the basket-shaped basic building unit as shown in Fig. 1(c). The basket-shaped building units are connected to each other *via* oxygens, in an alternate up-down manner, to form the three-dimensional architecture of **I**, with channels along the *b* axis ($7.7 \times 6.4 \text{ \AA}$; shortest atom-atom contact distances not including van der Waals radii) (Fig. 2). The amine molecules are present within these channels.

The Zn–O bond distances in the ZnO_4 tetrahedra in **I** are in the range 1.889–2.019 Å (av. 1.955 Å) and the P–O distances in the range 1.512–1.573 Å (av. 1.531 Å). The O–Zn–O angles are in the range 93.3–126.2° (av. 109.11°) and the O–P–O angles are in the range 107.2–113.6° (av. 109.46°). These geometric param-

eters are typical of those observed in open-framework zinc phosphates. The terminal nitrogen atoms of the amine molecule are disordered with an occupancy of 0.5.

Fig. 3 shows a comparison of various structural motifs encountered in open-framework zinc phosphates with the Zn_4O_4 clusters found in the present study. Infinite Zn–O–Zn linear chains have been reported in a few Zn phosphates.³ Tetrahedral OZn_4 building units are found in framework phosphates and arsenates⁴ and this feature has been observed recently in zinc 1,4-benzenedicarboxylate.⁶ The Zn_4O_4 tetramer obtained in this study, however, is unique, manifesting itself in the form of a four-membered ring structure. This ring structure is not unlike the four-membered $\text{M}_2\text{P}_2\text{O}_4$ ring commonly observed in open-framework phosphates, and considered to be the basic building unit of these materials.⁷ The formation of the four-membered Zn_4O_4 clusters in **I**, is a result of the presence of three-coordinate oxygens. The formation of such M–O clusters with transition elements might create a situation wherein it would be possible to synthesize materials possessing magnetic channels.

Notes and references

- 1 A. K. Cheetham, G. Ferey and T. Loiseau, *Angew. Chem., Int. Ed.*, 1999, **38**, 3268 and references therein.
- 2 S. Neeraj, S. Natarajan and C. N. R. Rao, *New J. Chem.*, 1999, **23**, 303.
- 3 S. Neeraj, S. Natarajan and C. N. R. Rao, *Chem. Mater.*, 1999, **10**, 1390; S. Natarajan, S. Neeraj and C. N. R. Rao, *Solid State Sci.*, 2000, **2**, 89.
- 4 W. T. A. Harrison, R. W. Broach, R. A. Bedard, T. E. Gier, X. Bu and G. D. Stucky, *Chem. Mater.*, 1996, **8**, 691; W. T. A. Harrison, M. L. F. Phillips, A. V. Chavez and T. M. Nenoff, *J. Mater. Chem.* 1999, **9**, 3087.
- 5 Crystal data for $[\text{N}_3\text{C}_4\text{H}_{16}][\text{Zn}_5(\text{PO}_4)_4]\text{I}$: $M = 812.93$, monoclinic, space group $P2_1/n$ (no. 14), $a = 15.934(6)$, $b = 7.403(9)$, $c = 16.209(2)$ Å, $\beta = 111.9(1)$, $V = 1774.52(11)$ Å³, $Z = 4$, $D_c = 3.043$ g cm⁻³, $\mu(\text{Mo-K}\alpha) = 7.117$ mm⁻¹. A total of 7021 data collected and merged to give 2548 unique reflections ($R_{\text{int}} = 0.056$) of which 1873 is considered to be observed [$I > 2\sigma(I)$]. The structure was solved and refined using SHELXTL-PLUS.⁸ Final $R_1 = 0.045$, $wR_2 = 0.094$, $S = 1.061$ were obtained for 263 parameters. CCDC reference number 186/2069. See <http://www.rsc.org/suppdata/dt/b0/b004245p/> for crystallographic files in .cif format.
- 6 H. Li, M. Eddaoudi, M. O'Keeffe and O. M. Yaghi, *Nature*, 1999, **402**, 276.
- 7 S. Ayyappan, S. Natarajan, A. K. Cheetham and C. N. R. Rao, *J. Solid State Chem.*, 1998, **139**, 207; S. Neeraj, S. Natarajan and C. N. R. Rao, *J. Solid State Chem.*, 2000, **150**, 417.
- 8 G. M. Sheldrick, SHELXTL-PLUS, Siemens Analytical X-Ray Instruments, Madison, WI, 1990.